

Ab initio phonon calculations for $\text{Ca}_5\text{Ir}_3\text{O}_{12}$

Kazuma NAKAMURA

*Quantum Physics Section, Kyushu Institute of Technology
1-1 Sensui-cho, Tobata, Kitakyushu, Fukuoka, 804-8550*

The title compound has recently attracted attention as a thermoelectric material because it has a relatively high Seebeck coefficient. In this study, we report an ab initio study about electronic and phononic properties for $\text{Ca}_5\text{Ir}_3\text{O}_{12}$. In particular, we investigated the effect of spin-orbit interaction (SOI) on the low-energy properties [1].

Density functional calculations with plane-wave basis sets were performed using the xTAPP code [2], where the ultrasoft pseudopotential and the generalized gradient approximation (GGA) of the exchange correlation potential were employed. The cutoff energies in the wavefunction and charge densities were 64 and 256 Ry, respectively, and the SOI was explicitly considered. To study the effects of SOI, we performed the usual GGA calculation and compared it with the result including the SOI. Below, we refer to the former as GGA and to the latter as SO-GGA. The atomic and lattice parameters were optimized with an $8 \times 8 \times 8$ k-point sampling, and we found that SO-GGA reproduces the experimental crystal structure quite well. The Fermi-surface calculations were performed with the dense $21 \times 21 \times 63$ k-point sampling to obtain the detailed surface structure [3]. Phonon calculations were performed using $11 \times 11 \times 11$ k-point sampling for a $1 \times 1 \times 3$ supercell [4].

Figure 1(a) shows our calculated band structure. To see the SOI effect, the SO-GGA band (thick red curves) is compared with the GGA band (thin blue curves) in Fig. 1(b). An appreciable difference can be observed in the low-energy bands; the GGA result exhibits metal-

lic bands, particularly along the L-M or H-K lines. When the SOI is switched on, the metallic bands are split and a pocket-like band structure appears. The gap size due to the SOI is about 0.3 eV, which is comparable to the valence bandwidth 0.5 eV.

Figures 1(c) and 1(d) show the Fermi surfaces based on the SO-GGA and GGA, respectively. We see that the GGA Fermi surface is contributed from the two bands (indicated in dark-blue and bright-red colors), while the SO-GGA Fermi surface is basically formed by the one band; the SOI makes the bright-red colored GGA Fermi surface disappear. In the SO-GGA Fermi surface, since the SOI resolves the band degeneracy, the Fermi surfaces are seemingly two (dark-blue and bright-blue colored surfaces); however, these two are originated from the same band. Also, in the SO-GGA Fermi surface, we see a sheet structure along the c^* -axis (the Γ -A line), which indicates a nesting trend along this direction. We note that the SOI is relevant to the narrowing of the sheet separation between the blue colored Fermi surfaces.

Figures 2(a) and 2(b) are our calculated phonon dispersions with and without SOI, respectively, and Fig. 2(c) is a comparison of two densities of states. Considering the SOI, the density of state is blue shifted as a whole, and a gap is formed around 10 THz. We found that phonon frequencies at the Γ point are in a good agreement with the Raman measurement.

As another achievement, we have released a new software RESPACK [5] that is a

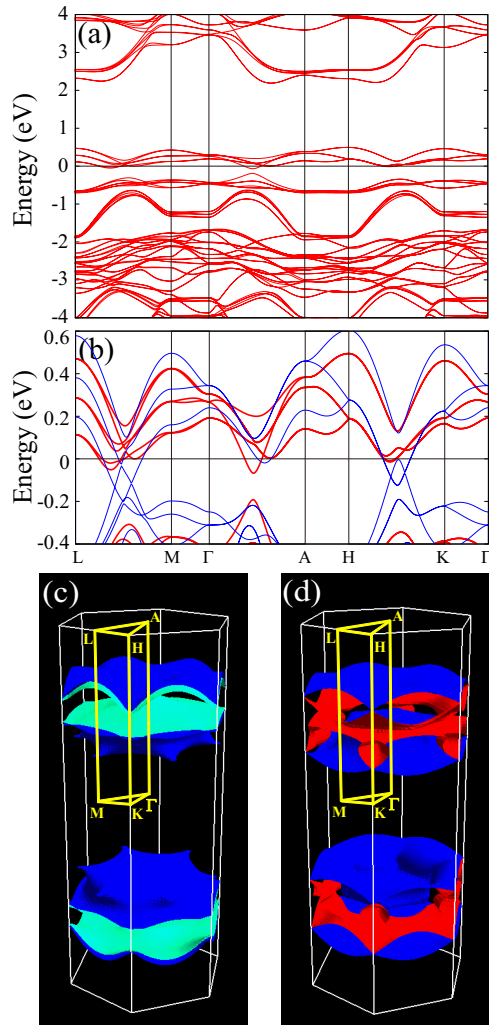


Figure 1: (Color online) (a) Ab initio electronic band structure considering the SOI in $\text{Ca}_5\text{Ir}_3\text{O}_{12}$. The energy zero is the Fermi level. (b) A zoom of the low-energy band structure, where the SO-GGA result (thick red curves) is compared with the usual GGA result (thin blue curve). (c) Calculated Fermi surface for SO-GGA and (d) GGA.

first-principles calculation program to evaluate the maximally localized Wannier functions, the RPA response functions, and frequency-dependent electronic interaction parameters.

References

- [1] K. Matsuhira, K. Nakamura, Y. Yasukuni, Y. Yoshimoto, D. Hirai, Z. Hiroi:

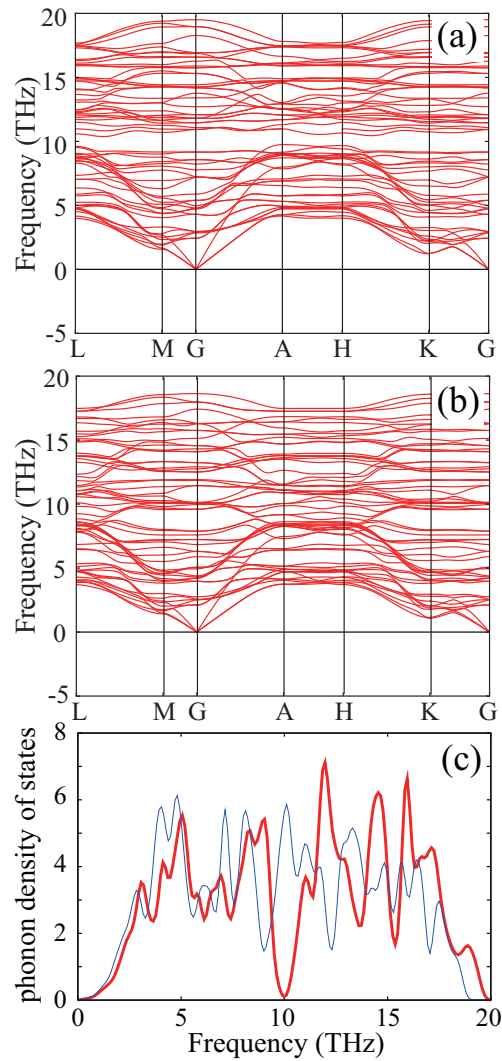


Figure 2: (Color online) (a) Ab initio phonon dispersion with the SOI in $\text{Ca}_5\text{Ir}_3\text{O}_{12}$. (b) The result without SOI. (c) Calculated phonon density of states, where the SO-GGA result (thick red curves) is compared with the usual GGA result (thin blue curve).

J. Phys. Soc. Jpn. **87** (2018) 013703.

- [2] <http://xtapp.cp.is.s.u-tokyo.ac.jp>
 [3] <http://fermisurfer.osdn.jp>
 [4] <https://atztogo.github.io/phonopy>
 [5] <https://sites.google.com/view/kazuma7k6r>